


HENAN YALONG SUPERHARO MATERIALS CO;LTD 16-5A NO.43 ZHONGYUAN WEST ROAD ZHENG ZHOU P.C.450007 CHINA TEL:86-371-67650359 FAX:86-371-67650319		D50=1.95+_0.20	Date: 01/09/21 Meas #:N/A Time: 14:02 Pres #: N/A
		Summary	Percentiles
		mv = 2.165	5% = 1.246 60% = 2.242
		mn = 1.654	10% = 1.423 70% = 2.407
		ma = 1.988	30% = 1.815 80% = 2.617
		cs = 3.019	40% = 1.961 90% = 2.957
		sd = 0.577	50% = 2.099 95% = 3.301
		Dia	Vol% Width
		2.099	100% 1.154

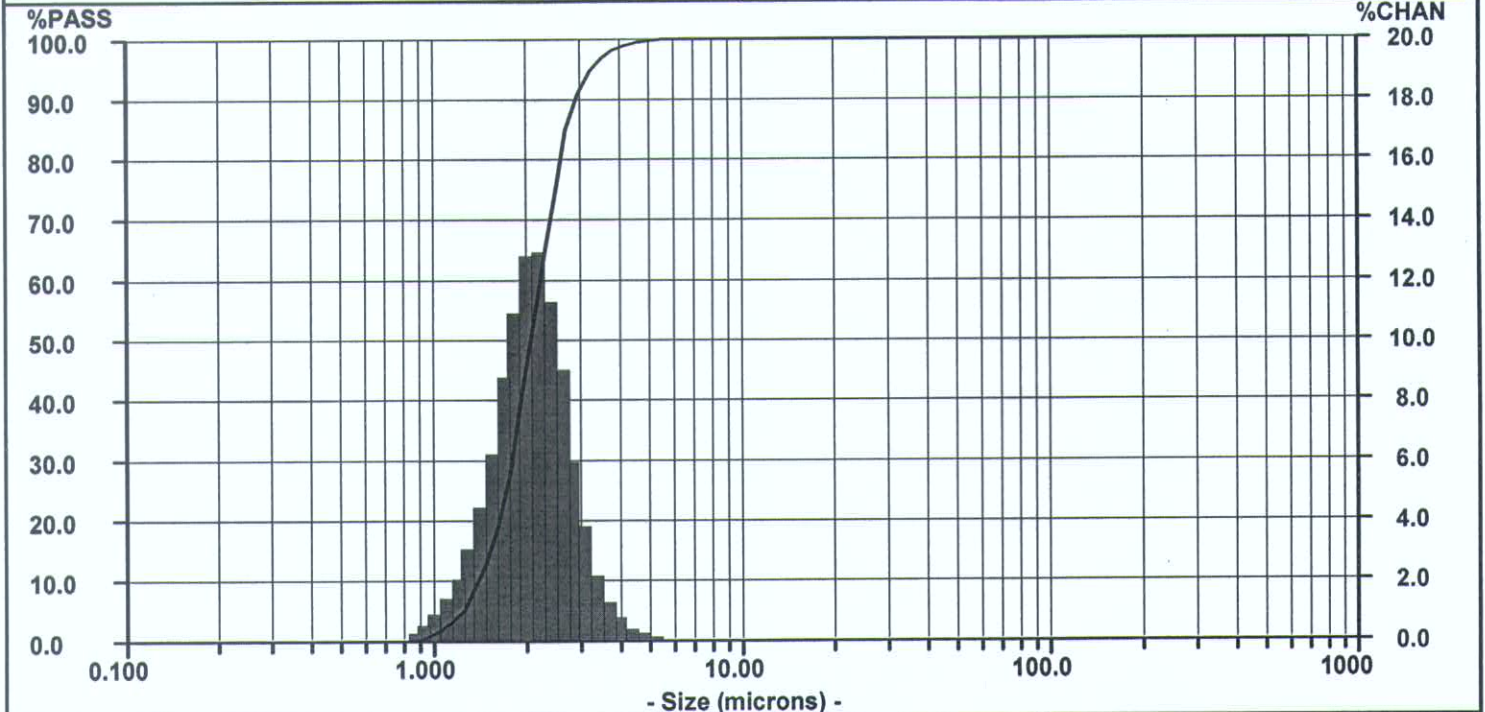

SIZE	%PASS	%CHAN	SIZE	%PASS	%CHAN	SIZE	%PASS	%CHAN	SIZE	%PASS	%CHAN
704.0	100.00	0.00	80.70	100.00	0.00	9.250	100.00	0.00	1.060	1.81	0.92
645.6	100.00	0.00	74.00	100.00	0.00	8.482	100.00	0.00	0.972	0.89	0.59
592.0	100.00	0.00	67.86	100.00	0.00	7.778	100.00	0.00	0.892	0.30	0.30
542.9	100.00	0.00	62.23	100.00	0.00	7.133	100.00	0.00	0.818	0.00	0.00
497.8	100.00	0.00	57.06	100.00	0.00	6.541	100.00	0.00	0.750	0.00	0.00
456.5	100.00	0.00	52.33	100.00	0.00	5.998	100.00	0.00	0.688	0.00	0.00
418.6	100.00	0.00	47.98	100.00	0.00	5.500	100.00	0.18	0.630	0.00	0.00
383.9	100.00	0.00	44.00	100.00	0.00	5.044	99.82	0.31	0.578	0.00	0.00
352.0	100.00	0.00	40.35	100.00	0.00	4.625	99.51	0.46	0.530	0.00	0.00
322.8	100.00	0.00	37.00	100.00	0.00	4.241	99.05	0.77	0.486	0.00	0.00
296.0	100.00	0.00	33.93	100.00	0.00	3.889	98.28	1.29	0.446	0.00	0.00
271.4	100.00	0.00	31.11	100.00	0.00	3.566	96.99	2.27	0.409	0.00	0.00
248.9	100.00	0.00	28.53	100.00	0.00	3.270	94.72	3.83	0.375	0.00	0.00
228.2	100.00	0.00	26.16	100.00	0.00	2.999	90.89	6.01	0.344	0.00	0.00
209.3	100.00	0.00	23.99	100.00	0.00	2.750	84.88	9.00	0.315	0.00	0.00
191.9	100.00	0.00	22.00	100.00	0.00	2.522	75.88	11.31	0.289	0.00	0.00
176.0	100.00	0.00	20.17	100.00	0.00	2.312	64.57	12.94	0.265	0.00	0.00
161.4	100.00	0.00	18.50	100.00	0.00	2.121	51.63	12.82	0.243	0.00	0.00
148.0	100.00	0.00	16.96	100.00	0.00	1.945	38.81	10.91	0.223	0.00	0.00
135.7	100.00	0.00	15.56	100.00	0.00	1.783	27.90	8.75	0.204	0.00	0.00
124.5	100.00	0.00	14.27	100.00	0.00	1.635	19.15	6.31	0.187	0.00	0.00
114.1	100.00	0.00	13.08	100.00	0.00	1.499	12.84	4.44	0.172	0.00	0.00
104.7	100.00	0.00	12.00	100.00	0.00	1.375	8.40	3.09	0.158	0.00	0.00
95.96	100.00	0.00	11.00	100.00	0.00	1.261	5.31	2.09	0.145	0.00	0.00
88.00	100.00	0.00	10.09	100.00	0.00	1.156	3.22	1.41	0.133	0.00	0.00

Distribution: Volume	RunTime: 10 seconds	Fluid: Water
Progression: Geometric Root8	Run Number 1 of 1 runs	Fluid Refractive Index: 1.33
Upper Edge: 704.0	Particle: W 0.5	Loading Factor: 0.0140
Lower Edge: 0.122	Particle Transparency: Trans	Transmission: 0.95
Residuals: Disabled	Particle Refractive Index: 2.41	Above Residual: 0.00
Number Of Channels: 100	Particle Shape: Irregular	Below Residual: 0.00
X100 Extended Range: No		
Filter: On	Database Path: N/A	