


测量详细信息	
Sample Name	Average of '0 -0.5 639码'

测量详细信息	
Measurement Date Time	2020/3/27 19:19:42
Result Source	Averaged

分析	
Particle Name	Diamond
Particle Refractive Index	2.418
Particle Absorption Index	0.010
Dispersant Name	Water
Dispersant Refractive Index	1.330
Scattering Model	Mie
<b>Analysis Model</b>	General Purpose
Weighted Residual	1.71 %
Laser Obscuration	7.44 %

结果	
Concentration	0.0003 %
Span	1.381
Uniformity	0.427
Specific Surface Area	12870 m <sup>2</sup> /kg
D [3,2]	0.466 μm
D [4,3]	0.590 μm
Dv (10)	0.268 μm
Dv (50)	0.533 μm
Dv (90)	1.00 μm

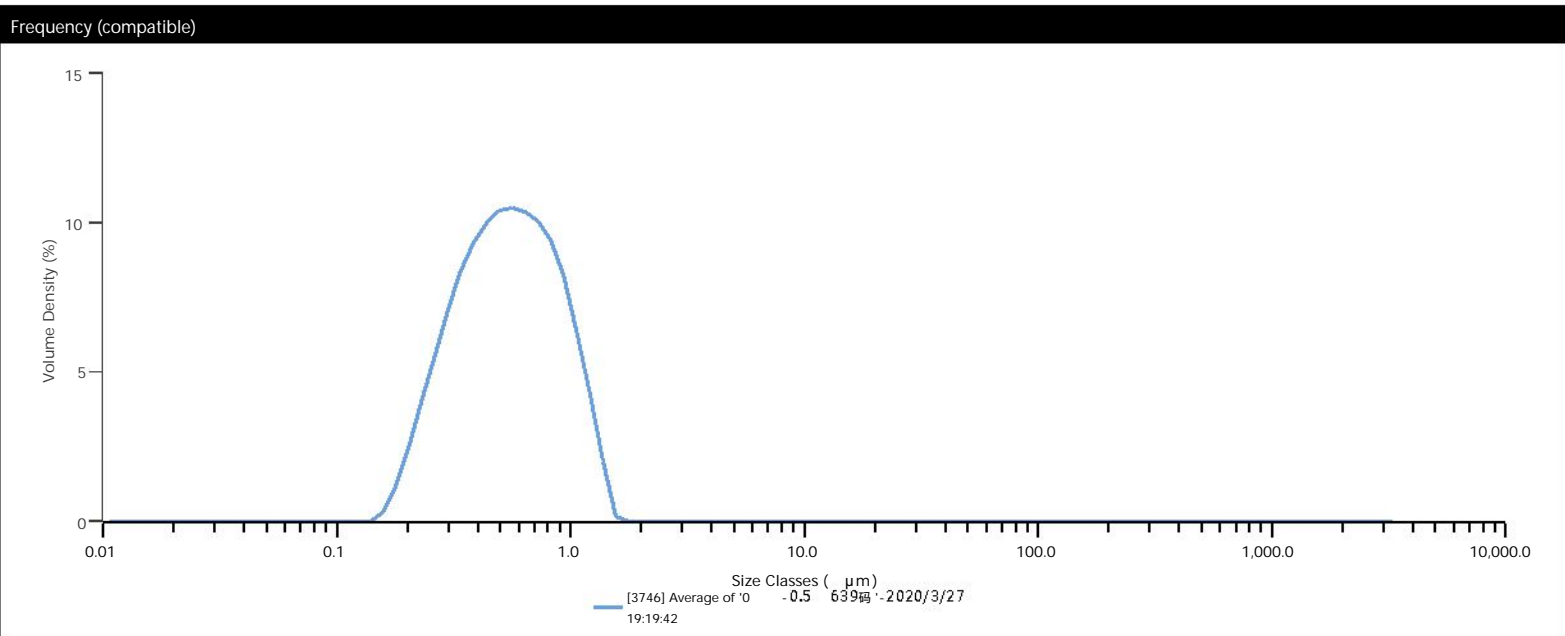

Result											
Size (μm)	% Volume In	Size (μm)	% Volume In	Size (μm)	% Volume In	Size (μm)	% Volume In	Size (μm)	% Volume In	Size (μm)	% Volume In
0.0100	0.00	0.0876	0.00	0.767	7.92	6.72	0.00	58.9	0.00	516	0.00
0.0114	0.00	0.0995	0.00	0.872	6.95	7.64	0.00	66.9	0.00	586	0.00
0.0129	0.00	0.113	0.00	0.991	5.40	8.68	0.00	76.0	0.00	666	0.00
0.0147	0.00	0.128	0.00	1.13	3.53	9.86	0.00	86.4	0.00	756	0.00
0.0167	0.00	0.146	0.23	1.28	1.67	11.2	0.00	98.1	0.00	859	0.00
0.0189	0.00	0.166	0.93	1.45	0.00	12.7	0.00	111	0.00	976	0.00
0.0215	0.00	0.188	2.04	1.65	0.00	14.5	0.00	127	0.00	1110	0.00
0.0244	0.00	0.214	3.32	1.88	0.00	16.4	0.00	144	0.00	1260	0.00
0.0278	0.00	0.243	4.55	2.13	0.00	18.7	0.00	163	0.00	1430	0.00
0.0315	0.00	0.276	5.78	2.42	0.00	21.2	0.00	186	0.00	1630	0.00
0.0358	0.00	0.314	6.96	2.75	0.00	24.1	0.00	211	0.00	1850	0.00
0.0407	0.00	0.357	7.82	3.12	0.00	27.4	0.00	240	0.00	2100	0.00
0.0463	0.00	0.405	8.36	3.55	0.00	31.1	0.00	272	0.00	2390	0.00
0.0526	0.00	0.460	8.72	4.03	0.00	35.3	0.00	310	0.00	2710	0.00
0.0597	0.00	0.523	8.77	4.58	0.00	40.1	0.00	352	0.00	3080	0.00
0.0679	0.00	0.594	8.66	5.21	0.00	45.6	0.00	400	0.00	3500	0.00
0.0771	0.00	0.675	8.41	5.92	0.00	51.8	0.00	454	0.00		