


HENAN YALONG SUPERHARO MATERIALS CO;LTD D50=3.50+0.30 Date: 03/11/24 Meas #: N/A
 16-5A NO.43 ZHONGYUAN WEST ROAD Time: 10:33 Pres #: N/A
 ZHENG ZHOU P.C.450007 CHINA
 TEL:86-371-67650359
 FAX:86-371-67650319

Summary	Percentiles	Dia	Vol%	Width	
mv = 3.856	5% = 2.617	60% = 3.917	3.705	100%	1.664
mn = 3.293	10% = 2.829	70% = 4.172			
ma = 3.650	30% = 3.320	80% = 4.499			
cs = 1.644	40% = 3.513	90% = 5.039			
sd = 0.832	50% = 3.705	95% = 5.613			

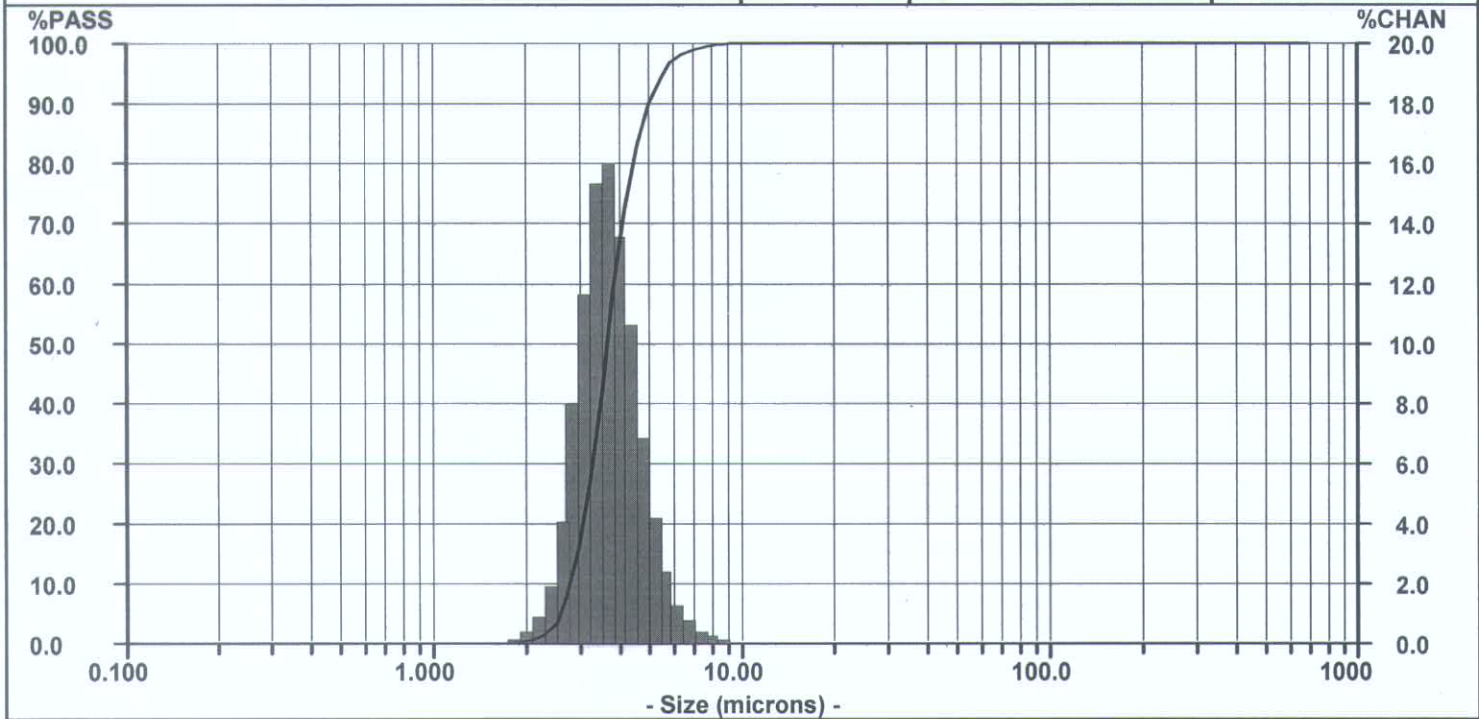

SIZE	%PASS	%CHAN	SIZE	%PASS	%CHAN	SIZE	%PASS	%CHAN	SIZE	%PASS	%CHAN
704.0	100.00	0.00	80.70	100.00	0.00	9.250	100.00	0.17	1.060	0.00	0.00
645.6	100.00	0.00	74.00	100.00	0.00	8.482	99.83	0.31	0.972	0.00	0.00
592.0	100.00	0.00	67.86	100.00	0.00	7.778	99.52	0.48	0.892	0.00	0.00
542.9	100.00	0.00	62.23	100.00	0.00	7.133	99.04	0.81	0.818	0.00	0.00
497.8	100.00	0.00	57.06	100.00	0.00	6.541	98.23	1.39	0.750	0.00	0.00
456.5	100.00	0.00	52.33	100.00	0.00	5.998	96.84	2.50	0.688	0.00	0.00
418.6	100.00	0.00	47.98	100.00	0.00	5.500	94.34	4.26	0.630	0.00	0.00
383.9	100.00	0.00	44.00	100.00	0.00	5.044	90.08	6.92	0.578	0.00	0.00
352.0	100.00	0.00	40.35	100.00	0.00	4.625	83.16	10.66	0.530	0.00	0.00
322.8	100.00	0.00	37.00	100.00	0.00	4.241	72.50	13.67	0.486	0.00	0.00
296.0	100.00	0.00	33.93	100.00	0.00	3.889	58.83	16.03	0.446	0.00	0.00
271.4	100.00	0.00	31.11	100.00	0.00	3.566	42.80	15.36	0.409	0.00	0.00
248.9	100.00	0.00	28.53	100.00	0.00	3.270	27.44	11.71	0.375	0.00	0.00
228.2	100.00	0.00	26.16	100.00	0.00	2.999	15.73	8.05	0.344	0.00	0.00
209.3	100.00	0.00	23.99	100.00	0.00	2.750	7.68	4.14	0.315	0.00	0.00
191.9	100.00	0.00	22.00	100.00	0.00	2.522	3.54	1.94	0.289	0.00	0.00
176.0	100.00	0.00	20.17	100.00	0.00	2.312	1.60	0.90	0.265	0.00	0.00
161.4	100.00	0.00	18.50	100.00	0.00	2.121	0.70	0.38	0.243	0.00	0.00
148.0	100.00	0.00	16.96	100.00	0.00	1.945	0.32	0.21	0.223	0.00	0.00
135.7	100.00	0.00	15.56	100.00	0.00	1.783	0.11	0.11	0.204	0.00	0.00
124.5	100.00	0.00	14.27	100.00	0.00	1.635	0.00	0.00	0.187	0.00	0.00
114.1	100.00	0.00	13.08	100.00	0.00	1.499	0.00	0.00	0.172	0.00	0.00
104.7	100.00	0.00	12.00	100.00	0.00	1.375	0.00	0.00	0.158	0.00	0.00
95.96	100.00	0.00	11.00	100.00	0.00	1.261	0.00	0.00	0.145	0.00	0.00
88.00	100.00	0.00	10.09	100.00	0.00	1.156	0.00	0.00	0.133	0.00	0.00

Distribution: Volume	RunTime: 10 seconds	Fluid: Water
Progression: Geometric Root8	Run Number 1 of 1 runs	Fluid Refractive Index: 1.33
Upper Edge: 704.0	Particle: W 0.5	Loading Factor: 0.0193
Lower Edge: 0.122	Particle Transparency: Trans	Transmission: 0.95
Residuals: Disabled	Particle Refractive Index: 2.41	Above Residual: 0.00
Number Of Channels: 100	Particle Shape: Irregular	Below Residual: 0.00
X100 Extended Range: No		
Filter: On	Database Path: N/A	Efficiency Shift: -4.00
		Function Shift: 2.02